


## Intro


The magnetic field profile at the interface of the ferromagnet  $\text{La}_{2/3}\text{Ca}_{1/3}\text{MnO}_2$  (LCMO) and the superconductor  $\text{YBa}_2\text{Cu}_3\text{O}_7$  (YBCO) in superlattices has been studied by specular ( $q_z$ -scan) and off-specular ( $\omega$ -scan) neutron reflectometry.

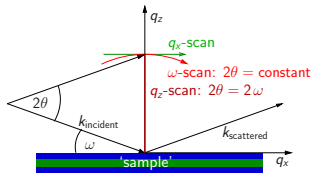


$q_z$  is normal to the sample surface, in-plane structure is averaged over several  $\mu\text{m}$ .  
 $q_x$  probes lateral inhomogeneities (interface roughness and domains).

These investigations were motivated by Low-Energy  $\mu\text{SR}$  and bulk magnetization measurements which showed an unexpected magnetic behaviour below  $T_c$ :

magnetisation




Low-Energy  $\mu\text{SR}$




The depth-resolution of these methods (if any) is not sufficient to allocate the increased magnetic flux to certain regions.

## Neutron Reflectometry


Unpolarised neutron-reflectometry  
 Morpheus@SINQ instrument  
 $[\text{YBCO}(100 \text{ \AA})/\text{LCMO}(100 \text{ \AA})]_7$  sample  
 cooled and measured in  $H = 100 \text{ Oe}$

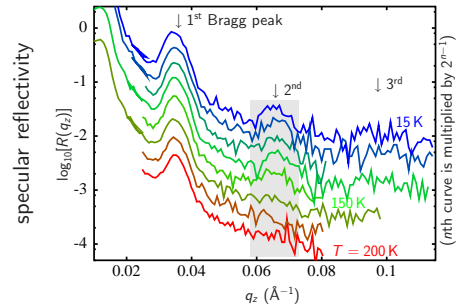


$I(q_z, T)$  map for the 1<sup>st</sup> and 2<sup>nd</sup> Bragg peaks

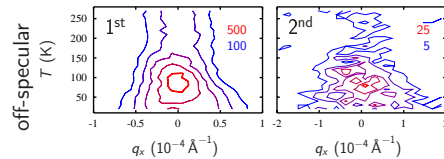

Bragg peak intensities

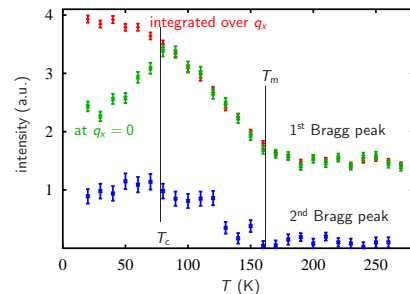


Specular reflectivity for polarised neutrons  
 ADAM@ILL  
 $[\text{YBCO}(150 \text{ \AA})/\text{LCMO}(140 \text{ \AA})]_6$  sample

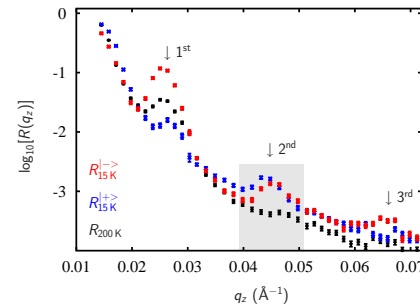


- change of 1<sup>st</sup> Bragg peak intensity below  $T_m$   
 $\Rightarrow$  increased contrast for  $| - \rangle$  neutrons  
 decreased contrast for  $| + \rangle$  neutrons
- 2<sup>nd</sup> Bragg peak forbidden by symmetry of  $V^{\text{nuclear}}$   
 $\Rightarrow B$  has an other  $z$ -dependence than  $V^{\text{nuclear}}$   
 (see simulations)
- $I_{\text{specular}} \propto I_{\text{integrated}}$  for  $T > T_c$   
 $\Rightarrow$  no detectable magnetic roughness
- $I_{\text{specular}} < I_{\text{integrated}}$  for  $T < T_c$   
 $\Rightarrow$  increasing magnetic roughness
- exchange bias  
 $\Rightarrow$  AFM layers must be present at the interface

## Simulation

Calculated with the computer code EDXR of P. Mikulík.

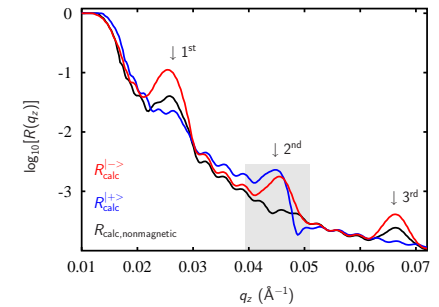

Suitable model potentials:

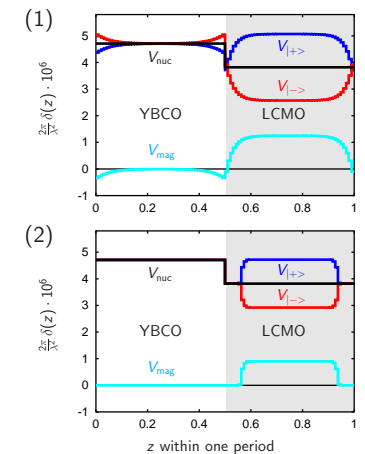

## Summary

Evidence for a characteristic difference between the structural and magnetic depth profiles is obtained from the occurrence of a structurally forbidden Bragg peak in the FM state and the anomalous temperature dependence of the intensity of the first Bragg peak.

The comparison with simulated spectra allows us to identify two possible magnetization profiles:  
 (1) A sizable magnetic moment develops within the SC layer that is antiparallel to the one in the FM layer.  
 (2) A significant "dead" region in the FM layer that has no net magnetic moment.

Both are compatible with exchange bias. Scenario (1) is supported by an anomalous SC-induced enhancement of the off-specular reflection which testifies for a strong mutual interaction of SC and FM order parameters and may be the signature of a spatially inhomogeneous SC/FM interface state.

## Magnetometry

SQUID measurement by F. Treubner, Uni. Konstanz — thanks!

